



On biaxiality of photoinduced structures in azopolymer films

A. KISELEV¹, O. YAROSHCHUK², Yu. ZAKREVSKYY²,
A. TERESHCHENKO²

¹ Chernigiv Technological University, Shevchenko Street 95, 14027 Chernigiv, Ukraine

² Institute of Physics of NASU, pr. Nauki 46, 03028 Kyiv, Ukraine

Spatial orientational structures in the layers of liquid crystalline polymalonates are investigated using UV absorption method and the results of null ellipsometry technique. Preferential in-plane alignment of azobenzene fragments and in-plane reorientation under irradiation with polarized UV light are established. The components of the order parameter tensor of azobenzene fragments are estimated for the initial state and after different doses of irradiation. The uniaxial as well as biaxial order of the azobenzene chromophores are detected. The biaxiality is observed in the intermediate stages of irradiation, whereas the uniaxial order is realized in the saturated state. The proposed theory takes into account biaxiality of the induced structures and describes well experimental dependencies of the order parameter components on the time of irradiation.

Key words: *azopolymer, photo-induced anisotropy, spatial orientation.*

PACS: *61.30.Gd, 4265.-k, 78.66.Qn*

1. INTRODUCTION

The photoinduced anisotropy (POA) in azopolymer films is a well-known phenomenon extremely promising for application in the systems of optical storage and computing, telecommunication, holography etc. [1]. Besides, photooriented polymer layers are excellent aligning substrates for liquid crystals [2]. Microscopic origin of POA in azopolymers is assumed to be a photoinduced orientational ordering of azobenzene moieties in the direction perpendicular to polarization direction of the exciting light \mathbf{E} . Mechanisms of such orientational ordering are described elsewhere [1, 3]. As far as spatial case is concerned, there are many directions perpendicular to \mathbf{E} . The variety of orientational 3D structures (uniaxial, biaxial, splayed with different spatial orientation of the principle axes) can be observed depending on many factors such as chemical structure, method of film preparation, irradiation conditions and so on. The study of the 3D orientational structures in polymer films was restrained with the lack of effective experimental methods. The known approaches [

4, 5] are associated with limited field of application and strong approximations. For the sake of simplicity, in the experimental studies [1, 6, 7] and even in theoretical calculations [3] uniaxial ordering had been assumed. The first attempt to estimate the biaxiality was by Wiesner *et al.* [5] that used the results of IR absorption. The weak point of the approach [5] is that it can be applied only for the special orientational configuration and requires knowledge of the original orientational structure. We used this method to process the data of UV absorption. On the other hand, the method of null ellipsometry is complementary to the UV spectroscopic measurements. By using it we estimated [8, 9] the type of the 3D orientational configuration before irradiation and after subsequent periods of irradiation. These results combined with the UV absorption measurements allowed us to estimate the components of order parameter tensor of azobenzene chromophores. Our theoretical approach to the photoinduced ordering in azopolymers is based on kinetic rate equations extended to take into consideration biaxiality of the induced structures. As a result we computed the order parameter components of azobenzene units for different irradiation doses. Predictions of the theory are in good agreement with the data obtained experimentally.

2. EXPERIMENTAL

2.1. Samples

We used poly[octyl(4-hexyloxy-4'-nitro)azobenzenemalonate] synthesis of which is described in [10]. The polymer was solved in dichloroethane and spincoated on the quartz slabs. The prepared films were kept at the room temperature for 24 h for the evaporation of solvent. To induce anisotropy in the films, we used the irradiation of a Hg lamp. Intensity of the actinic light was about 4.0 mW. A Glan-Thomson polarizer was applied for the polarization of UV light. A normal incidence of the actinic light was used in our studies. The irradiation was provided in several steps followed by absorption measurements.

2.2. Method

The UV/Vis absorption measurements were carried out using PC conjugated spectrometer KSVU (LOMO, Russia). The wavelength of testing light was tuned to the absorption maximum of azobenzene fragments. The testing beam was polarized and directed normally to film plane. Absorption components in the direction of exciting light polarization \mathbf{E} and perpendicularly to \mathbf{E} were measured. We denote them as D_x and D_y , respectively. The out-of-plane absorption component, D_z , was estimated by making use the method proposed in [5]. The latter assumes that the sample has uniaxial structure with in-plane position of the axis of anisotropy at the instant of time t_0 . It implies that $D_z(t_0) = D_x(t_0)$ and the total (spatial) absorption can be estimated as follows

$$D_{total} = D_x(t_0) + D_y(t_0) + D_z(t_0) = 2D_x(t_0) + D_y(t_0). \quad (1)$$

When the number of *trans* azobenzene units does not change considerably, the total absorption is constant and the value of D_z at instant of time t can be determined from the following equation:

$$D_z(t) = D_{total} - D_x(t) - D_y(t), \quad (2)$$

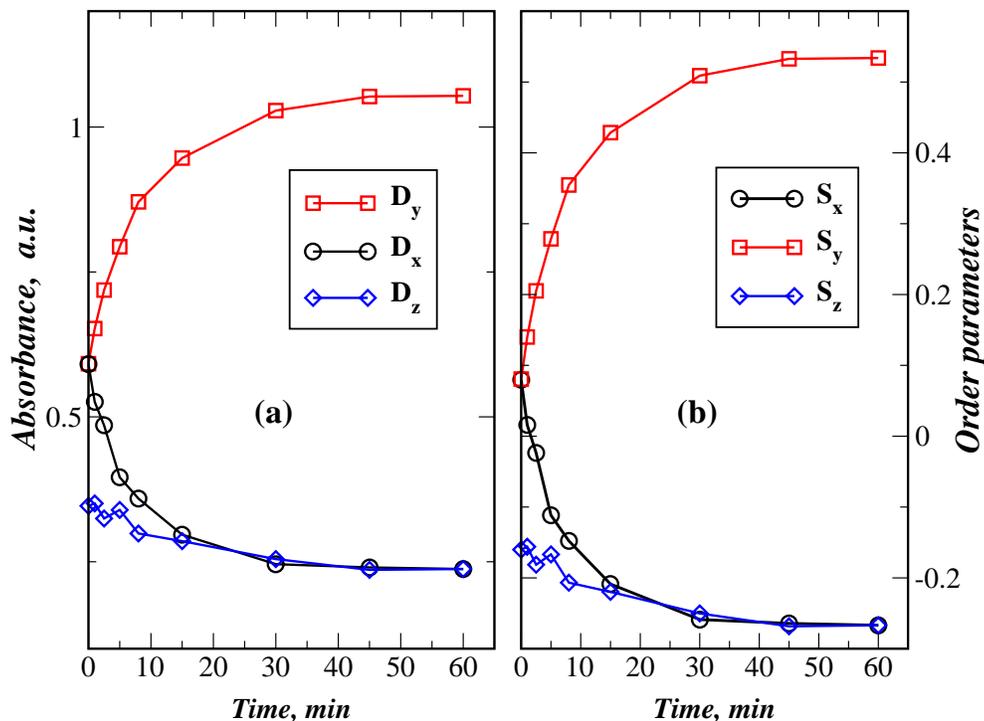


Figure 1. Dependencies of (a) the principle absorption coefficients and (b) components of the order parameter on irradiation time.

where $D_x(t)$ and $D_y(t)$ are experimentally measured parameters.

2.3. Results and discussion

The UV/Vis spectra of studied compound have intensive absorption band with the maximum at $\lambda_t = 377$ nm corresponding to $\pi\pi^*$ transition of *trans* azobenzene fragments. The wavelength of the testing beam was tuned to this value. After switching off actinic light the spectrum revealed changes that became stationary for approximately 5 min. In order to have the azobenzene units relaxed to the stationary state, the components D_x and D_y were measured in 15 min after each irradiation period.

In order to estimate a lifetime of *cis* isomers we have measured relaxation of the spectral changes at $\lambda_t = 377$ nm after irradiation with non-polarized light. Incidence directions of both actinic and testing light were approximately normal to the film. It was found that the relaxation curve contains two components with characteristic

times of 0.5 s and 4 min, respectively. The first value can be attributed to *cis* - *trans* transition of azobenzene chromophores, whereas the second one corresponds to orientational relaxation of the units.

The experimentally measured absorption components D_x and D_y for different irradiation doses are presented in Fig. 1a. Kinetics of D_x and D_y is typical for reorientation mechanism of azobenzene units [3]. Both curves $D_x(t)$ and $D_y(t)$ reveal saturation. As it was earlier shown by null ellipsometry method [8, 9], the saturated state of the film of studied polymer is fitted as uniaxial structure with the in-plane orientation of the axis of anisotropy. Taking it into account and additionally assuming that lifetime of *cis* form is about 0.5 s we arrive at the conclusion that, in our experimental case, the method described above can be applied to estimate D_z . The values of D_z calculated by means of Eqs. (1)-(2) are also presented in Fig. 1a. Dependencies $D_x(t)$, $D_y(t)$ and $D_z(t)$ show that the photoinduced ordering is mainly due to the in-plane reorientation of azobenzene fragments in the y direction. In addition, slight reorientation from x to z direction is observed.

The orientational structure in general case is described by the tensor S_{ij} , which is diagonal when the coordinate axes directed along the principle axes of the film. The diagonal elements $S_{xx} \equiv S_x$, $S_{yy} \equiv S_y$ and $S_{zz} \equiv S_z$ are related to the absorption components D_x , D_y and D_z [5]. For example,

$$S_x = \frac{2D_x - (D_y + D_z)}{2(D_x + D_y + D_z)}. \quad (3)$$

The components S_y and S_z can be obtained by the cyclic permutation in the expression (3). The values of S_x , S_y and S_z calculated using equation (3) are presented in Fig. 1b. It is seen that initial stage of irradiation is characterized by biaxiality, whereas the photosaturated stage by uniaxial orientation with order parameter about 0.7. According to [9], the uniaxiality of the saturated state could be caused by mesomorphic properties of azobenzene fragments. The action of actinic light then can be considered as a factor stimulated selforganization peculiar to mesophases [11]. From this point of view, the realized structure is a result of photoreorientation and selfassembling processes in the film.

3. THEORY

In this section we discuss briefly our theoretical approach to kinetics of the photoinduced reorientation. Starting from the master equations, we then specialize the rates of involved transitions. The final kinetic equations for order parameters are derived after making assumptions on the form of angular redistribution probabilities. In addition, this phenomenological model includes a set of order parameters that characterizes main chain orientation of the polymer.

3.1. Master equations

In what follows we shall assume that the dye molecules in the ground state are of *trans* form with the orientation of the molecular axis defined by the unit

vector $\hat{\mathbf{n}}$. The latter is specified by the polar, θ , and azimuthal, ϕ , angles: $\hat{\mathbf{n}} = (\sin \theta \cos \phi, \sin \theta \sin \phi, \cos \theta)$.

Angular distribution of the *trans* molecules is characterized by the distribution function $F_{tr}(\hat{\mathbf{n}})$. Molecules in the excited state have the *cis* conformation and the corresponding distribution function is $F_{cis}(\hat{\mathbf{n}})$. Then for the number of *trans* and *cis* molecules we have

$$N_{tr} = \int F_{tr}(\hat{\mathbf{n}}) d\hat{\mathbf{n}}, \quad N_{cis} = \int F_{cis}(\hat{\mathbf{n}}) d\hat{\mathbf{n}}, \quad N = N_{tr} + N_{cis}, \quad (4)$$

respectively, and N is the total number of molecules.

Introducing the normalized distribution functions $f_1(\hat{\mathbf{n}}) \equiv F_{tr}/N$ and $f_2(\hat{\mathbf{n}}) \equiv F_{cis}/N$, we write the kinetic rate equations of the following general form [12, 13]:

$$\frac{\partial f_i}{\partial t} = \left[\frac{df_i}{dt} \right]_{\text{Diff}} + \sum_{j=1}^2 \int [W_{ij}(\hat{\mathbf{n}}, \hat{\mathbf{n}}') f_j(\hat{\mathbf{n}}', t) - W_{ji}(\hat{\mathbf{n}}', \hat{\mathbf{n}}) f_i(\hat{\mathbf{n}}, t),] d\hat{\mathbf{n}}', \quad (5)$$

where $i = 1, 2$. The first term on the right hand side of Eq. (5) is due to rotational diffusion of molecules in *trans* ($i = 1$) and *cis* ($i = 2$) conformations, so that the terms proportional to W_{ii} can be incorporated into the diffusion term. The remaining part of Eq. (5) accounts for *trans-cis* (terms proportional to W_{21}) and *cis-trans* (terms proportional to W_{12}) transitions.

The *trans-cis* transition is stimulated by the incident UV-light quasisresonant to the corresponding transition. Assuming that the electromagnetic wave is linearly polarized along the x -axis, the rate of the transition can be written as follows [3, 14]:

$$W_{21}(\hat{\mathbf{n}}, \hat{\mathbf{n}}') = \Gamma_{tr}(\hat{\mathbf{n}}, \hat{\mathbf{n}}') P_{tr}(\hat{\mathbf{n}}'), \quad (6)$$

$$P_{tr}(\hat{\mathbf{n}}') = \Phi_{tr \rightarrow cis} \sum_{i,j} \sigma_{ij}^{(tr)}(\hat{\mathbf{n}}') E_i E_j^* = q_t I (1 + u n_x^2), \quad (7)$$

where $\sigma^{(tr)}(\hat{\mathbf{n}})$ is the tensor of absorption cross section for *trans* molecule oriented along $\hat{\mathbf{n}}$: $\sigma_{ij}^{(tr)} = \sigma_{\perp}^{(tr)} \delta_{ij} + (\sigma_{\parallel}^{(tr)} - \sigma_{\perp}^{(tr)}) n_i n_j$, $u \equiv (\sigma_{\parallel}^{(tr)} - \sigma_{\perp}^{(tr)}) / \sigma_{\perp}^{(tr)}$ and $\Phi_{tr \rightarrow cis}$ is the quantum yield of the process; $\Gamma_{tr}(\hat{\mathbf{n}}, \hat{\mathbf{n}}')$ describes the angular redistribution of molecules excited in the *cis* state; I is the pumping intensity.

For the *cis-trans* transition along the same line of arguments we have

$$W_{12}(\hat{\mathbf{n}}, \hat{\mathbf{n}}') = (\gamma_c + q_c I) \Gamma_c(\hat{\mathbf{n}}, \hat{\mathbf{n}}'), \quad q_c \equiv \Phi_{cis \rightarrow trans} \sigma^{(cis)}, \quad (8)$$

where $\gamma_c \equiv 1/\tau_c$, τ_c is the life time of *cis* molecule and the anisotropic part of absorption cross section is disregarded, $\sigma_{\parallel}^{(cis)} = \sigma_{\perp}^{(cis)} \equiv \sigma^{(cis)}$.

3.2. Order parameters

The following three order parameters are of our primary concern:

$$S_x = \langle 3n_x^2 - 1 \rangle / 2 \equiv -S_0/2 + \sqrt{3/2} S_2, \quad (9a)$$

$$S_y = \langle 3n_y^2 - 1 \rangle / 2 \equiv -S_0/2 - \sqrt{3/2} S_2, \quad (9b)$$

$$S_z = \langle 3n_z^2 - 1 \rangle / 2 \equiv S_0, \quad (9c)$$

where $\langle \Psi \rangle \equiv \int \Psi f_1 d\hat{\mathbf{n}}$.

We can now expand the distribution functions $f_i(\hat{\mathbf{n}})$ over spherical functions and derive equations for the corresponding components. The next step involves truncating the system and computing the kernels of angular redistribution. Omitting the details, in the simplest case, we have the following system of kinetic equations:

$$\frac{\partial n}{\partial t} = -(\gamma_c + q_c I) n + \bar{q}_t I (1 - n + \bar{u} S_x), \quad (10a)$$

$$\begin{aligned} \frac{\partial S_i}{\partial t} = & -\bar{q}_t I \left[\sum_{j=0,2} w_{ij} S_j - v(1 - n)(\delta_{i,0} - \sqrt{3/8} \delta_{i,2}) \right] - \\ & - (\bar{q}_t I + D_t)(S_i - S_i^{(p)}) + (\gamma_c + q_c I) \Gamma_c C_i, \end{aligned} \quad (10b)$$

$$\frac{\partial C_i}{\partial t} = -(\gamma_c + q_c I + D_c) C_i, \quad (10c)$$

$$\frac{\partial S_i^{(p)}}{\partial t} = \gamma_p (S_i - S_i^{(p)}), \quad i = 0, 2, \quad (10d)$$

where $n \equiv N_{cis}/N$, $\bar{q}_t \equiv q_t(1 + u/3)$, $\bar{u} \equiv 2u/(3 + u)$, $v \equiv \bar{u}[10\pi]^{-1/2}$, $w_{22} = -w_{00} = \bar{u}/7$, $w_{02} = -2w_{20} = \sqrt{6} w_{00}$; $D_c \equiv 6D_r^{(cis)}$ and $D_t \equiv 6D_r^{(tr)}$ are rotational diffusion constants of *cis* and *trans* molecules, respectively. Additional order parameters C_i and $S_i^{(p)}$ characterize ordering of intermediate states of *cis* molecules and ordering of polymer backbone [15], respectively.

3.3. Steady state

Eqs. (10) yield the uniaxial stationary state with

$$S_x^{(st)} = S_z^{(st)} = S_0^{(st)} \iff S_2^{(st)} = \sqrt{3/2} S_0^{(st)}.$$

The result is

$$S_0^{(st)} = \frac{\alpha v}{w_{00} + \sqrt{3/2} w_{02} + \beta v}, \quad 1 - n_{st} = \alpha - \beta S_0^{(st)}, \quad (11)$$

where

$$\alpha = \frac{\gamma_c + q_c I}{\gamma_c + (q_c + \bar{q}_t) I}, \quad \beta = \frac{\bar{u} \bar{q}_t I}{\gamma_c + (q_c + \bar{q}_t) I}.$$

According to Fig. 1b, experimental data give $S_z^{(st)} = S_y^{(st)} \approx -0.267$. Assuming that $u = 19$, $\sigma^{(cis)} \approx \sigma_{\perp}^{(tr)}$, and $q_t/q_c \approx 30$ (see [15]), as it is shown in Fig. 2, the relevant steady state order parameters can be calculated from Eq. (11).

Referring to Fig. 2, it is seen that the experimental value of S_z corresponds to $\gamma_c \approx 2.68 \bar{q}_t I$. From Eq. (11) we can now calculate n_{st} : $n_{st} \approx 0.14$. According to [3, 14], the mechanism of reorientation in our case, where fraction of *cis* molecules in photosteady state is found to be relatively small, corresponds to angular redistribution.

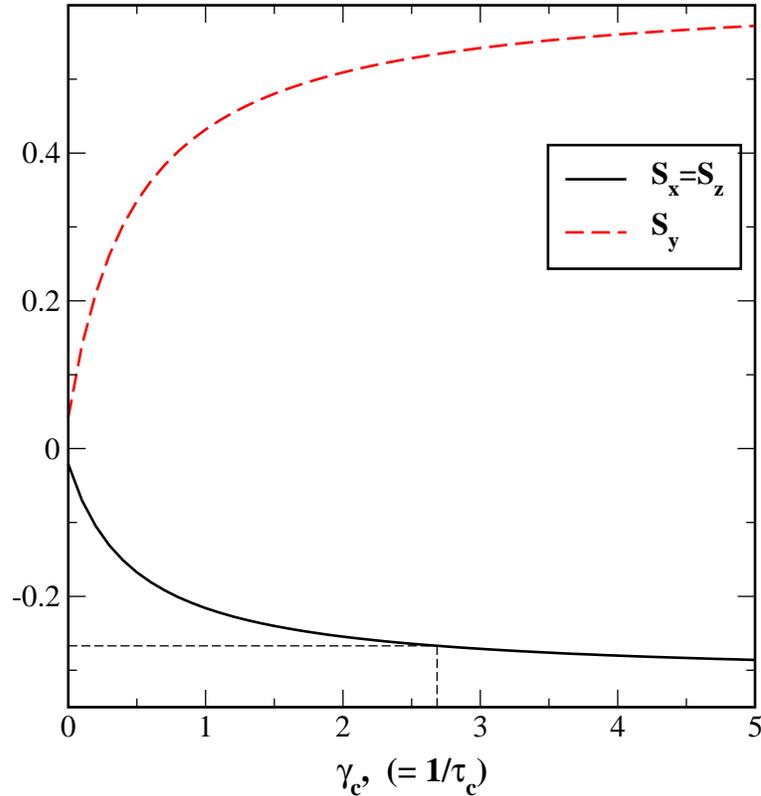


Figure 2. Stationary value of S_z vs $\gamma_c \equiv 1/\tau_c$ computed from Eq. (11). The life time of *cis* molecules is scaled by $\bar{q}_t I$. The marked point corresponds to the experimental steady state value of S_z , $S_z^{(st)} \approx -0.267$.

4. CONCLUSIONS

We have thus demonstrated that UV absorption method supplemented by the null ellipsometry technique is an effective tool for investigation of the features of spatial ordering in azopolymer films. This method is shown to detect spatial rearrangement of chromophores under irradiation. In addition, it enables us to calculate the components of order parameter tensor for the original structures of the films as well as for structures at various stages of irradiation.

Our theoretical approach to the kinetics of photoinduced reorientation is based on master equations with allowance for biaxiality. Predictions of the simple phenomenological model proposed in this paper are in good agreement with experimental data as far as kinetics of order parameters and photosteady state are concerned.

Despite, for brevity, the details of underlying theoretical considerations had been almost completely left aside this paper, it should be emphasized that angular redistribution is of crucial importance in our approach. Moreover, in order to account for long term stability of the photoinduced isomerization more sophisticated treatment would involve development of an effective medium theory. We will publish more comprehensive discussion of the theory elsewhere.

Acknowledgment

We gratefully acknowledge financial support from U.S. Civilian Research & Development Foundation.

References

1. Eich M., Wendorff H., Reck B., and Ringsdorf H.// *Macromol. Chem., Rapid Commun.*, 1987, vol. 8, p. 59.
2. Gibbons W.M., Shannon P.J., Sun S.-T., and Swetlin B.J.// *Nature*, 1991, vol. 351, p. 49.
3. Dumont M. and Sekkat Z.// *SPIE*, 1992, vol. 1774, p. 188.
4. Blinov L.M., Dubinin N.V., Rumyantsev V.G., and Yudin S.G.// *Sov. Optika i spektroskopiya*, 1983, vol. 55, No. 4, p. 679 (in Russian).
5. Wiesner U., Reynolds N., Boeffel Ch., and Spiess H.W.// *Liq. Cryst.*, 1992, vol. 11, No. 2, p. 251.
6. Kulinna C., Hvilsted S., Hendann C., Siesler H., and Ramanujam P.S.// *Macromolecules*, 1998, vol. 31, p. 2141.
7. Natansohn A., Rochon P., Meng X., Barrett C., Buffeteau T., Bonenfant S., and Pezolet M.// *Macromolecules*, 1998, vol. 31, p. 1155.
8. Chien L.-C., Kelly J., Lindau J., Sergan T., and Yaroshchuk O. – In: *Abstracts of OLC'99, Puerto Rico (USA)*, 26 September – 1 October 1999, p.42.
9. Yaroshchuk O., Sergan T., Lindau J., Lee S.N., Kelly J., Chien L.-C.// *Mol. Cryst. Liq. Cryst.*, 2000 (to be published).
10. Böhme A., Novotna E., Kresse H., Kuschel F., and Lindau J.// *Macromol. Chem.*, 1993, vol. 194, p. 3341.
11. Fisher Th., Läsker L., Czaplá S., Stumpe J.// *Mol. Cryst. Liq. Cryst.*, 1997, vol. 299, p. 299.
12. van Kampen N.G. *Stochastic Processes in Physics and Chemistry*. Amsterdam, North – Holland Physics Publishing, 1984.
13. Gardiner C.W. *Handbook of Stochastic Methods*. Berlin, Springer – Verlag, 1985.
14. Dumont M. – In: *Photoactive Organic Materials*, eds. Kajzar et al., Netherlands, Kluwer Academic Publishers, 1996, p. 501.
15. Puchkovskaya G.A., Reshetnyak V.Yu., Tereshchenko A.G., Yaroshchuk O.V., Lindau J.// *Mol. Cryst. Liq. Cryst.*, 1998, vol. 321, p. 31.

Про двовісність фотоіндукованих структур в азополімерних плівках

О. Кисельов¹, О. Ярощук², Ю. Закревський², О. Терещенко²

¹ Чернігівський технологічний університет, вул. Шевченка 95, 14027
Чернігів, Україна

² Інститут фізики НАНУ, проспект Науки 46, 03028 Київ, Україна

Шляхом використання методу УФ поглинання та результатів еліпсометричних вимірювань вивчені просторові орієнтаційні структури в шарах рідкокристалічних полімерів. Встановлено, що під дією поляризованого УФ випромінювання азобензольні фрагменти орієнтуються переважно в площині. Отримано оцінку для компонентів тензора параметра порядку як у початковому стані, так і після різних доз опромінювання. Виявлено як одновісне так і двовісне впорядкування азобензольних хромофорних груп. Причому двовісність спостерігається у проміжній стадії опромінювання, тоді як одновісний стан реалізується в режимі насичення. Запропонована теорія враховує двовісність індукованих структур і добре описує експериментальні залежності компонентів параметра порядку від часу опромінювання.

Ключові слова: азополімер, фотоіндукована анізотропія, просторова орієнтація.

PACS: 61.30.Gd, 4265.-k, 78.66.Qn